



# Corrosion inhibition of carbon steel in perchloric acid by potassium iodide

Tarik Attar <sup>1,2\*</sup>, Abbes Benchadli <sup>1</sup>, Esma Choukchou-Braham <sup>1</sup>

<sup>1</sup> Laboratory Toxicomed, University Abou Beker Belkaid Tlemcen, BP119, 13000 Tlemcen, Algeria

<sup>2</sup> Superior School of Applied Sciences of Tlemcen, BP 165, 13000 Bel Horizon, Tlemcen, Algeria

\*Corresponding author E-mail: [att.tarik@gmail.com](mailto:att.tarik@gmail.com)

## Abstract

Corrosion processes are responsible for numerous losses mainly in the industrial scope. It is clear that the best way to combat it is prevention. The effect of temperature on the corrosion behavior of carbon steel was studied by mass loss measurements in the temperature range 293–333 K. The inhibition efficiency increases with increasing temperature. The inhibitor showed 97.98 % inhibition efficiency at  $1.10^{-3}$  M concentration of iodide potassium in 1 M perchloric acid solutions. The values of activation energy ( $E_a$ ), enthalpy of activation ( $\Delta H_a$ ) and entropy of activation ( $\Delta S_a$ ), free energy of adsorption ( $\Delta G_{ads}$ ), enthalpy of adsorption ( $\Delta H_{ads}$ ) and entropy of adsorption ( $\Delta S_{ads}$ ) were calculated. The adsorption of this inhibitor on carbon steel surface obeys Langmuir adsorption isotherm.

**Keywords:** Corrosion Inhibition; Carbon Steel; Potassium Iodide; Weight Loss; Adsorption Isotherm.

## 1. Introduction

Carbon steels are the most commonly used construction materials and corrosion phenomena has become important particularly in acidic media because its employability are increased. Strong acids are widely used in industries for many purposes, especially in cleaning, descaling, pickling procedures, Oil Well acidizing and other applications isotherm (Abd El-Maksoud 2008). Therefore, protective measures should be required to reduce the corrosion rate in acids by using chemical and other means, among the different methods use of inhibitors is most commonly and economical (Al-Otaibi et al. 2014). A corrosion inhibitor is a chemical substance which, when added in small concentrations to an environment, minimizes or prevents corrosion (Riggs 1973; Uhlig et al. 1985). Inhibitors had great acceptance in the industries due to excellent anti-corrosive properties. The inhibition efficiency depends on the various parameters, corrosive medium, pH, temperature, duration of immersion, metal composition and on the nature of the inhibitor (Loto et al. 2012; Attar et al. 2014). Adsorption isotherms provide information about the interaction of the adsorbed molecules with the electrode surface (Bereket et al. 2002; attar et al. 2014). The adsorption of the inhibitors can be described by two main types of interaction: Physisorption and/or chemisorption (Xiumei et al. 2012; Zarrok et al. 2012): One is physical adsorption, which involves electrostatic forces between ionic charges or dipoles on the adsorbed species and the electric charge at the metal/solution interface. The heat of adsorption is low and therefore this type of adsorption is stable only at relatively low temperatures. The other is chemical adsorption, which involves charge transfer or sharing from the inhibitor molecules to the metal surface to form a coordinate type bond. This type of adsorption is known to have much stronger adsorption energy compared to the other mode of adsorption. Thus, such bond is more stable at higher temperatures. The weight loss method (gravimetric) is known to be the most widely used method of monitoring inhibition efficiency (Obot et al. 2010).

The aim of the present work is to study the inhibition efficiency of iodide potassium for the corrosion of carbon steel in perchloric acid medium 1M and to evaluate thermodynamic parameters of corrosion inhibition process for the adsorption of inhibitor on carbon steel metal surface.

## 2. Experimental

### 2.1. Material preparation

The test solutions of 1 M of Perchloric acid were prepared by the dilution of analytical grade 72%  $\text{HClO}_4$  with bi-distilled water in 50 mL. Steel XC38 containing in wt. %: 0.37 C, 0.68 Mn, 0.077 Cr, 0.059 Ni, 0.023 Si, 0.016 S, 0.011 Ti, 0.009 Co, 0.16 Cu, and iron is the remainder. The electrode was polished using different grades of emery papers after be polished, degreased and weighed. Each specimen was weighed using an analytical balance of 0.0001 g accuracy. All experiments are in triplicates and illustrated data are mean values of obtained results.

### 3. Results and discussion

#### 3.1. Effect of immersion time

The weight loss measurements were performed in 1 M HClO<sub>4</sub> in absence and presence of KI at 10<sup>-3</sup> M concentration for 30 min to 24 h immersion time at temperature of 303 K.

The inhibition efficiency (IE%) of potassium iodide was calculated using the formula (1).

$$IE(\%) = 100 * (W_{\text{corr}} - W_{\text{inh}}) / W_{\text{corr}} \quad (1)$$

Where  $W_{\text{corr}}$  and  $W_{\text{inh}}$  are the corrosion rates of carbon steel samples in the absence and presence of potassium iodide compound, respectively.

The corrosion rate (w) was calculated from the formula (2):

$$W = (m_1 - m_2) / S.t \quad (2)$$

Where  $m_1$  is the mass of the specimen before corrosion,  $m_2$  the mass of the specimen after immersion in solution, S the total area of the specimen and t the corrosion.

The variation of the inhibition efficiency of this inhibitor is almost constant from the first 60 minutes of immersion, which allowed us to say that the immersion time has no significant effect on the corrosion inhibition of carbon steel in M HClO<sub>4</sub>, is shown in Figure 1. The weight loss of carbon steel is nearly varied linearly with immersion period in the absence and presence of inhibitor as seen in Figure 2.

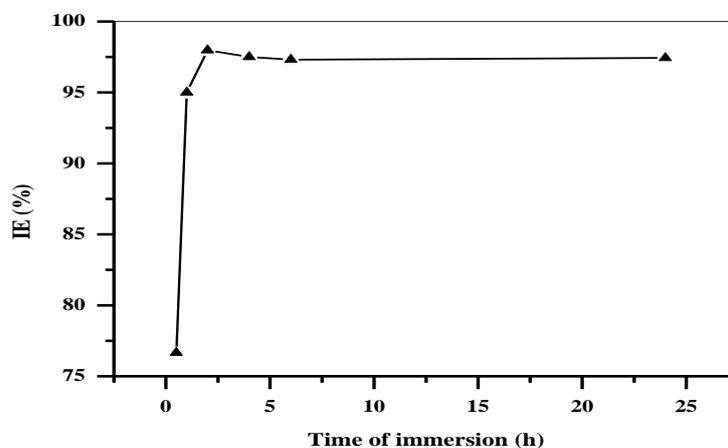


Fig. 1: Variation of the Inhibition Efficiency with Immersion Time for Carbon Steel 1M HClO<sub>4</sub> Containing 10<sup>-3</sup>M of KI at 303 K.

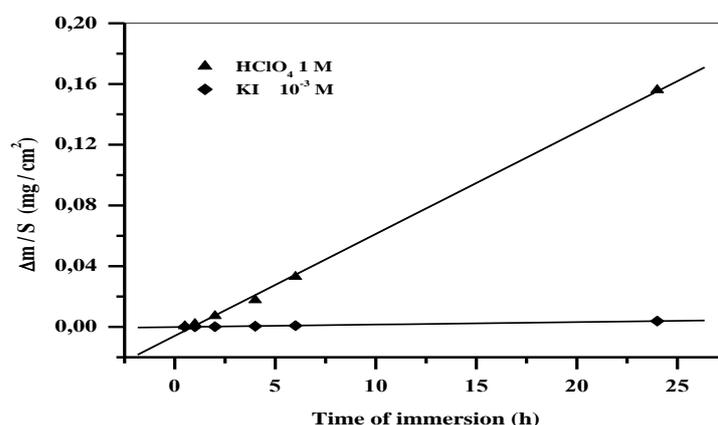


Fig. 2: Weight Loss Versus Immersion Time of XC38 in 1 M HClO<sub>4</sub> Without and with 10<sup>-3</sup> M of KI at 303 K.

#### 3.2. Effect of temperature

The effect of temperature on the inhibition effectiveness at various concentration of potassium iodide was studied in the temperature domain (293–333 K) at 2 h of immersion. The values of inhibition efficiency and corrosion rate obtained from weight loss method are showed in figure 3 and 4.

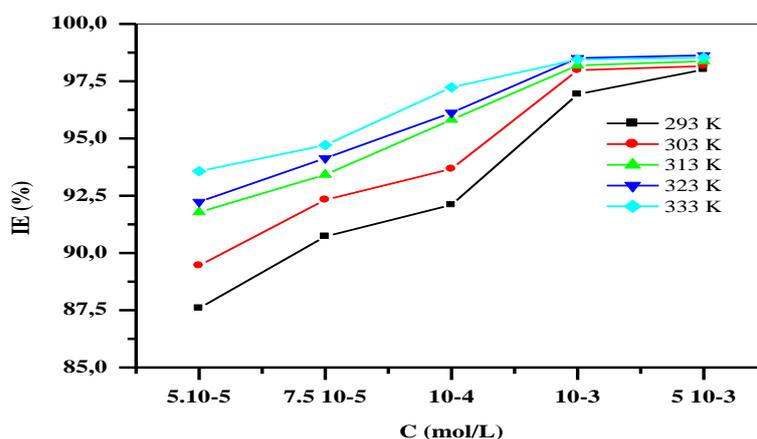


Fig. 3: Variation of Inhibition Efficiency (IE%) with Concentration of KI for Carbon Steel in 1 M HClO<sub>4</sub> at Different Temperatures.

The inhibition was estimated to be superior to 87.59 %, even at concentrations as low as  $5 \cdot 10^{-5}$  M, and the maximum efficiency of 97.98 % was recorded at  $10^{-3}$  M. The same study was carried out in the Hydrochloric acid where the maximum efficiency at  $10^{-3}$  M, was 59.37% and 6.25 % at low concentration ( $5 \cdot 10^{-5}$  M) (Benchadli et al. 2018). From the graph it is evident that the concentration change had only marginal influence on inhibition efficiency. It was also observed that corrosion rate decreased with increase in inhibitor concentration.

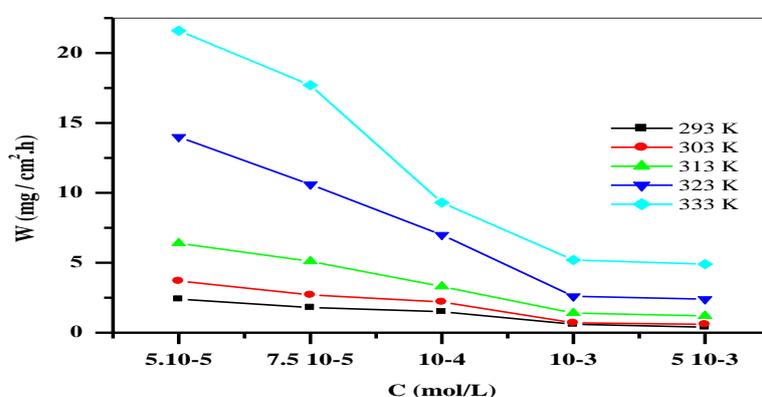


Fig. 4: Variation of Corrosion Rate with the Concentrations of KI for Carbon Steel in 1 M HClO<sub>4</sub> at Different Temperatures.

The study of the effect of temperature on the inhibition efficiency and corrosion rate facilitates the calculation of kinetic and thermodynamic parameters for the inhibition and the adsorption processes.

### 3.3. Thermodynamic parameters and adsorption isotherm

The adsorption is also influenced by the structure and the charge of the metal surface, and the type of testing electrolyte (Obot et al. 2009). In acid environment, the inhibitor acts generally by chemisorption and/or physical adsorption at the metal surface (Elmsellem et al. 2014). The inhibition of the corrosion of carbon steel in 1 M HClO<sub>4</sub> medium acid with addition of different concentrations of potassium iodide can be explained by the adsorption of the iodide ions on the metal surface. Inhibition efficiency was directly proportional to the fraction of the surface covered by the adsorbed molecules ( $\theta$ ). The values of the degree of surface coverage were evaluated at different concentrations of the inhibitors.

The degree of surface coverage ( $\theta$ ) was calculated using following equation (3):

$$\theta = 1 - (W_{inh}/W_{corr}) \quad (3)$$

The Langmuir adsorption isotherm plot for the adsorption of various concentrations of the inhibitor was shown in Figure 5. According to the Langmuir isotherm model (Benabdellah et al. 2006).

$$C_{inh}/\theta = C_{inh} + 1/K_{ads} \quad (4)$$

Where  $K_{ads}$  is the equilibrium constant of the equilibrium adsorption process. This isotherm assumes that adsorbed molecule occupies only one site and it does not interact with other adsorbed species (Abdel Hameed et al. 2011). The linear regression parameters between  $C_{inh}/\theta$  and  $C_{inh}$  are listed in Table 1. The strong correlation ( $R^2=1$ ) showed that the adsorption of the inhibitor molecules in 1M HClO<sub>4</sub> acid on the surface of electrode obeyed to the Langmuir's adsorption isotherm (Tang et al. 2003).

Table 1: Thermodynamic Parameters for the Adsorption of KI in HClO<sub>4</sub> Solution on Carbon Steel Electrodes at Different Temperatures.

T (K)	R <sup>2</sup>	10 <sup>4</sup> × K <sub>ads</sub> (L/mol)	ΔH <sub>ads</sub> (KJ/mol)	ΔG <sub>ads</sub> (KJ/mol)	ΔS <sub>ads</sub> (J/mol K)
293	1	12.966		-38,462	213.160
303	1	22.167	23,994 <sub>(eq.6)</sub>	-41,125	214.914
313	1	30.181		-43,286	214.952
323	1	33.240		-44,928	213.380
333	1	46.042	23,730 <sub>(eq.7)</sub>	-47,221	213.858

It can be observed that  $K_{ads}$  values increase with the increasing temperature. The high values of  $K_{ads}$  suggest that interaction between adsorbed molecules and the metal surface is strong, indicating that the inhibitor molecules are not easily removable from the surface by the solvent molecules (Desimone et al. 2011).

Adsorption equilibrium constant ( $K_{ads}$ ) and free energy of adsorption ( $\Delta G_{ads}$ ) were calculated using the following relationship (Fekry et al. 2010):

$$\Delta G_{ads} = -RT \ln (55.5 K_{ads}) \quad (5)$$

Where, 55.5 is the concentration of water in solution in mol/L and R is the universal gas constant and T is the absolute temperature.

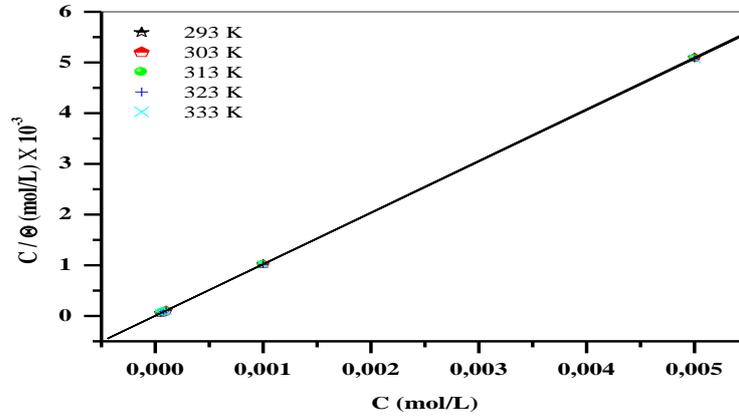


Fig. 5: Relationship between  $C_{inh}/\theta$  and Inhibitor Concentration  $C_{inh}$ .

To obtain the adsorption heat ( $\Delta H_{ads}$ ), the regression between  $\ln(K_{ads})$  and  $1/T$  (Figure 6) was dealt with and straight line obtained with slope equal to  $(-\Delta H_{ads}/R)$ . The adsorption heat could be calculated according to the Van't Hoff equation (Tang et al. 2003).

$$\ln K_{ads} = (-\Delta H_{ads}/RT) + \text{Const} \quad (6)$$

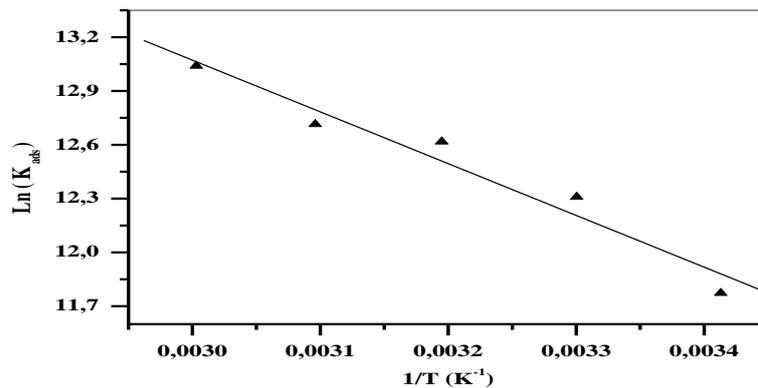


Fig. 6: Relationship between  $\ln(K_{ads})$  and  $1/T$  for Carbon Steel Corrosion in 1M  $HClO_4$  Solution with Potassium Iodide.

Generally, the values of adsorptive free enthalpy up to  $-20$  kJ/mol are consistent with the electrostatic interaction between the charged molecules and the charged metal (physisorption), while those negative values higher than  $-40$  kJ/mol involve sharing or transfer of electrons from the inhibitors to the metal surface to form a coordinate type of bond (chemisorption) (Bensajjay et al. 2003).

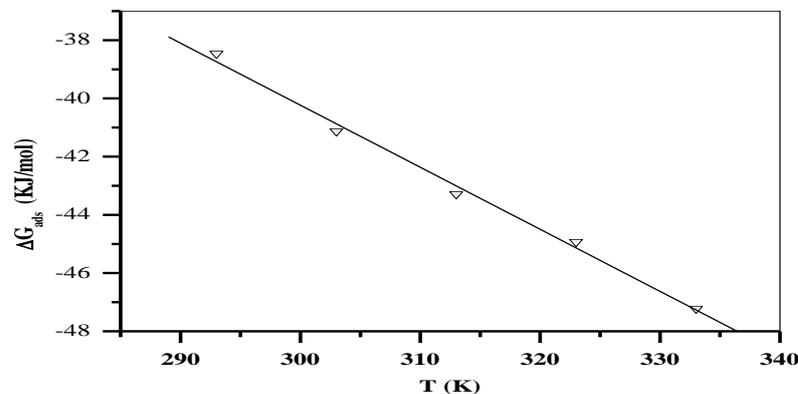


Fig. 7: Relationship between  $\Delta G_{ads}$  and Absolute Temperature.

$\Delta G_{ads}$  is related to the enthalpy change and entropy change of adsorption process,  $\Delta H_{ads}$  and  $\Delta S_{ads}$ , respectively by Gibbs equation

$$\Delta G_{ads} = \Delta H_{ads} - T\Delta S_{ads} \quad (7)$$

Using the obtained values of  $\Delta G_{\text{ads}}$  from the modified Langmuir isotherm, we can plot  $\Delta G_{\text{ads}}$  versus T (Fig. 7). These plots give straight lines with slopes ( $-\Delta S_{\text{ads}}$ ) and intercepts ( $\Delta H_{\text{ads}}$ ) (Hassan et al. 2007). The endothermic adsorption process ( $\Delta H_{\text{ads}} > 0$ ) is attributed unequivocally to chemisorption (Durnie et al. 1997). In the present case, the positive values of the enthalpy of adsorption indicate that the adsorption of the tested compounds is an endothermic process. The magnitude of  $\Delta G_{\text{ads}}$  values obtained from weight loss measurements was in the range of -38 to -47 kJ/mol which also shows chemisorptions of the inhibitor. Moreover the  $\Delta G_{\text{ads}}$  values increase with increasing temperature, which is due to the fact of strong chemisorption at higher temperatures.  $\Delta S_{\text{ads}}=213.21$  J/mol.K found by Gibbs equation. The value of  $\Delta S_{\text{ads}}$  is positive in the adsorption process indicating that the presence of inhibitor increases the solvent entropy (Hameed et al. 2011). The value of the enthalpy and entropy of adsorption found by the two methods such as Van't Hoff and Gibbs relations are in good agreement.

### 3.4. Kinetic parameters of activation

The Arrhenius equation is employed to study the effect of temperature on the rate of corrosion of carbon steel in acid media containing various concentrations of inhibitor as expressed by equation (8) (Singh et al. 2012; Attar et al. 2014).

$$w = A + \exp(-E_a / RT) \quad (8)$$

Where  $w$  is the corrosion rate of carbon steel,  $A$  is Arrhenius pre-exponential factor,  $E_a$  is the activation energy,  $R$  is the gas constant and  $T$  is the temperature

The activation energy ( $E_a$ ) at different concentrations of the inhibitor at various temperatures was determined by plotting  $\ln(w)$  Versus  $1/T$  (Figure 8).

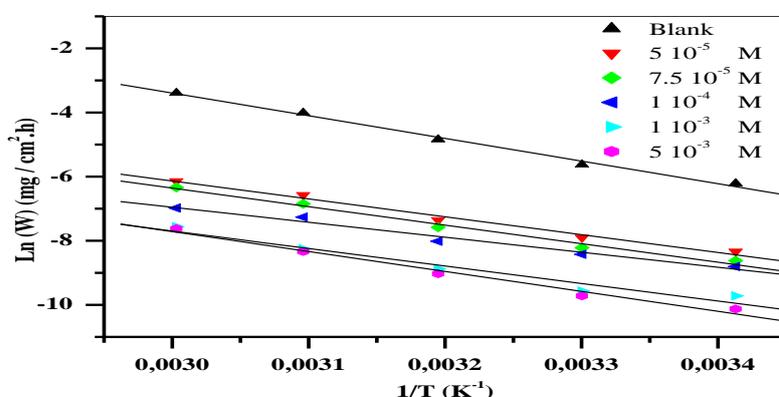


Fig. 8: Arrhenius Plot for the Dissolution of Carbon Steel in 1 M HClO<sub>4</sub> with and Without Inhibitor at Various Temperatures.

The enthalpy and entropy of activation for the metal dissolution process are determined using the transition state Eq. (9)

$$\ln(w/T) = -\Delta H_a/RT + \ln(RT/Nh) + (\Delta S_a/R) \quad (9)$$

Where  $h$  is Plank's constant and  $N$  is Avogadro's number  $R$  is the universal gas constant,  $\Delta H$  is the enthalpy of activation and  $\Delta S$  is the entropy of activation. A plot of  $\ln(w/T)$  versus  $1/T$  gave a straight line (Figure. 9) with slope ( $-\Delta H_a/R$ ) and intercept  $[\ln(R/Nh) + (\Delta S_a/R)]$ . From the plot, the values of  $\Delta H_a$  and  $\Delta S_a$  were calculated and tabulated in Table 3, (Correlation ( $R^2 > 0.98$ )).

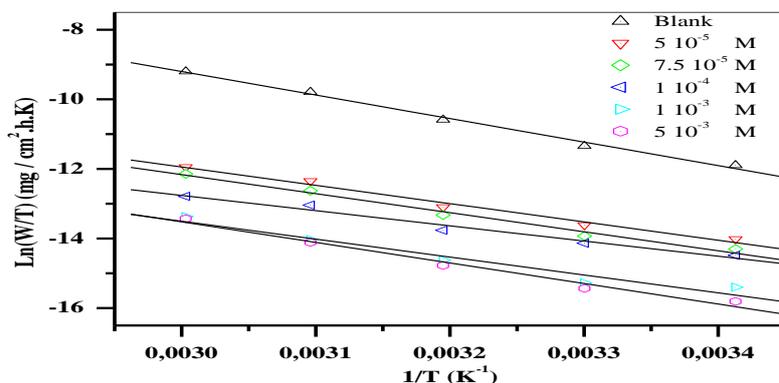


Fig. 9: Transition Arrhenius Plots of Carbon Steel in 1 M HClO<sub>4</sub> with and without Inhibitor at Various Temperatures.

Table 2: Activation Parameters for the Carbon Steel Dissolution in 1 M HClO<sub>4</sub> in Absence and Presence of Different Concentrations of KI

$C_{\text{inh}}$ (M)	$E_a$ (KJ/mol)	$\Delta H_a$ (KJ/mol)	$\Delta S_a$ (J/mol.K)	$\Delta H_{a313K} (=E_a - RT)$ (KJ/mol)	$\Delta G_{a313K}$ (KJ/mol)
0.0	58.794	56.200	-105,437	56.191	89.201
$5 \times 10^{-5}$	46.338	43.743	-165,622	43.785	95.582
$7.5 \times 10^{-5}$	48.053	45.459	-162,304	45.450	96.260
$10^{-4}$	38.914	36.320	-194,688	36.311	97.257
$10^{-3}$	45.376	42.782	-181,468	42.773	99.581
$5 \times 10^{-3}$	51.689	49.095	-162,677	49.086	100.012

Further, the values  $\Delta H_a$  obtained from the Eq. (9) and those values obtained from equation,  $\Delta H = E_a - RT$  are in good agreement with each other.

The change in activation free energy ( $\Delta G_a$ ) of the corrosion process can be calculated at each temperature by applying the equation:

$$\Delta G_a = \Delta H_a - T\Delta S_a \quad (10)$$

The values of the apparent activation energy  $E_a$  for the inhibited solutions are lower than that for the uninhibited one, indicating a chemisorption process of adsorption (Dehri et al. 2006). The positive sign of the enthalpies  $\Delta H_a$  reflects the endothermic nature of the steel dissolution process and that mean the dissolution of steel is difficult (Mohamed et al. 2015). The negative values of  $\Delta S_a$  in the inhibited and uninhibited systems imply that activation complex in the rate determining step represents an association rather than a dissociation step, meaning that a decrease disorder takes place on going from reactants to the activated complex (Abd El-Rehim et al. 2001). In corrosion context, the activation Gibbs free energy is the excess energy needed to transform metal atoms at the metal surface into solvated metal ions (David et al. 2010).

## 4. Conclusion

On the basis of the experimental results obtained in the present study, the following conclusions can be drawn.

- The protection efficiency of the inhibitor depends on its concentration, immersion time and temperature.
- The efficiency (IE%) increase with increasing concentration and temperature.
- The corrosion process was inhibited by adsorption of the inhibitor molecule on the carbon steel surface.
- Adsorption of inhibitor on carbon steel surface from 1 M HClO<sub>4</sub> obeys Langmuir adsorption isotherm.
- The negative values of  $\Delta G_{ads}$  showed the spontaneity of the adsorption.
- The inhibitor molecules adsorbed on the surface of carbon steel through chemisorption adsorption.

## References

- [1] Abd El-Maksoud SA, Fouda AS (2005), Some pyridine derivatives as corrosion inhibitors for carbon steel in acidic medium. *Materials Chemistry and Physics*, 93, 84-90. <https://doi.org/10.1016/j.matchemphys.2005.02.020>.
- [2] Al-Otaibi MS, Al-Mayouf AM, Khan M, Mousa AA, Al-Mazroa SA (2014), Corrosion inhibitory action of some plant extracts on the corrosion of mild steel in acidic media. *Arabian Journal of Chemistry*, 7, 340-346. <https://doi.org/10.1016/j.arabjc.2012.01.015>.
- [3] Riggs OL (1973), Corrosion Inhibitors (2nd edn), CC. Nathan, Houston.
- [4] Uhlig HH, Revie RW (1985), Corrosion and corrosion control. John Wiley & Sons, New York.
- [5] Loto RT, Loto CA, Popoola API (2012), Corrosion inhibition of thiourea and thiazole derivatives: a review. *Journal of Materials and Environmental Science*, 3, 885-894.
- [6] Attar T, Larabi L (2014), The Inhibition Effect of Potassium Iodide on the Corrosion of Pure Iron in Sulphuric Acid. *Advances in Chemistry*, 2014, 1-5. <https://doi.org/10.1155/2014/827514>.
- [7] Bereket G, Yurt A (2002), Inhibition of the corrosion of low carbon steel in acidic solution by selected quaternary ammonium compounds. *Anti-Corrosion Methods and Materials*, 49, 210-220. <https://doi.org/10.1108/00035590210431764>.
- [8] Attar T, Larabi L (2014), Corrosion inhibition of cold rolled steel in 0.5M H<sub>2</sub>SO<sub>4</sub> by potassium iodide. *Der Pharma Chemica*, 6, 181-186.
- [9] Xiumei W, (2012), The Inhibition Effect of Bis-Benzimidazole Compound for Mild Steel in 0.5 M HCl Solution. *Int. J. Electrochem Sci*, 7, 11149-11160.
- [10] Zarrak H, Zarrouk A, Salghi A, Ramli Y, Hammouti B (2012), Adsorption and Inhibition Effect of 3-Methyl-1-Propargylquinoxalin-2(1H)-One on Carbon Steel Corrosion in Hydrochloric Acid. *Int. J. Electrochem. Sci*, 7, 8958-8973.
- [11] Obot IB, Obi-Egbedi NO (2010), Adsorption properties and inhibition of mild steel corrosion in sulphuric acid solution by ketoconazole: Experimental and theoretical investigation. *Corros Sci*, 52, 198-204. <https://doi.org/10.1016/j.corsci.2009.09.002>.
- [12] Benchadli A, Attar T, Choukchou-Braham E (2018), Corrosion Inhibition of Carbon Steel (XC 38) in Hydrochloric Acid by Potassium Iodide. *Journal of Advanced Research in Science and Technology*, 5, 834-844.
- [13] Obot IB, Obi-Egbedi NO (2009), Umoren, Antifungal drugs as corrosion inhibitors for aluminium in 0.1 M HCl. *Corros. Sci*, 51, 1868-1875. <https://doi.org/10.1016/j.corsci.2009.05.017>.
- [14] Elmsellem H, Basbas N, Chetouani A, Aouniti A, Radi A (2014), Quantum Chemical Studies and Corrosion Inhibitive Properties of Mild Steel by Some Pyridine Derivatives in 1 N HCl Solution. *Portugaliae Electrochimica Acta*, 32, 77-108. <https://doi.org/10.4152/pea.20140207>.
- [15] Benabdellah M, Aouniti A, Dafali A, Hammouti B, Benkaddouret M (2006), Investigation of the inhibitive effect of triphenyltin 2-thiophene carboxylate on corrosion of steel in 2 M H<sub>3</sub>PO<sub>4</sub> solutions. *Applied Surface Science*, 252, 8341-8347. <https://doi.org/10.1016/j.apsusc.2005.11.037>.
- [16] Abdel Hameed RE (2011), Ranitidine Drugs as Non-Toxic Corrosion Inhibitors for Mild Steel in Hydrochloric Acid Medium. *Portugaliae Electrochimica Acta*, 29, 273-285. <https://doi.org/10.4152/pea.201104273>.
- [17] Tang LB, Mu GN, Liu GH (2003), The effect of neutral red on the corrosion inhibition of cold rolled steel in 1.0 M hydrochloric acid," *Corros. Sci*, 45, 2251-2262. <https://doi.org/10.3390/ma6062436>.
- [18] Desimone MP, Gordillo G, Simison SN (2011), The effect of temperature and concentration on the corrosion inhibition mechanism of an amphiphilic amido-amine in CO<sub>2</sub> saturated solution. *Corrosion Science*, 53, 4033-4043. <https://doi.org/10.1016/j.corsci.2011.08.009>.
- [19] Fekry AM, Ameer MA (2010), Corrosion Inhibition of Mild Steel in Acidic Media Using Newly Synthesized Heterocyclic Organic Molecules. *International Journal of Hydrogen Energy*, 35, 7641-7651. <https://doi.org/10.1016/j.ijhydene.2010.04.111>.
- [20] Tang LB, Mu GN, Liu GH (2003), The effect of neutral red on the corrosion inhibition of cold rolled steel in 1.0 M hydrochloric acid. *Corros. Sci*, 45, 2251-2262. [https://doi.org/10.1016/S0010-938X\(03\)00046-5](https://doi.org/10.1016/S0010-938X(03)00046-5).
- [21] Bensajjay E, Alehyen S, El Achouri M, Kertit S (2003), Corrosion inhibition of steel by 1phenyl 5mercapto 1,2,3,4tetrazole in acidic environments (0.5 M H<sub>2</sub>SO<sub>4</sub> and 1/3 M H<sub>3</sub>PO<sub>4</sub>). *Anti-Corros. Meth. Mater*, 50, 402-409. <https://doi.org/10.1108/00035590310501558>.
- [22] Hassan HH (2007), Inhibition of mild steel corrosion in hydrochloric acid solution by triazole derivatives: Part II: time and temperature effects and thermodynamic treatments. *Electrochim. Acta*, 53, 1722-1730. <https://doi.org/10.1016/j.electacta.2007.08.021>.
- [23] Durnie W, De Marco R, Jefferson A, Kinsella B (1999), Development of a Structure-Activity Relationship for Oil Field Corrosion Inhibitors. *J. Electrochem. Soc*, 146, 1751-1756. <https://doi.org/10.1149/1.1391837>.
- [24] Hameed RSA (2011), Aminolysis of polyethylene terephthalate waste as corrosion inhibitor for carbon steel in HCl corrosive medium. *Adv. App. Sci. Res.*, 2, 483-499.
- [25] Singh A, Ahamad I, Yadav DK, Singh VK, Quraishi MA (2012), The effect of environmentally benign fruit extract of shahjan (moringa oleifera) on the corrosion of mild steel in hydrochloric acid solution. *Chemical Engineering Communications*. 199, 63-77. <https://doi.org/10.1080/00986445.2011.570390>.

- [26] Attar T, Larabi L, Yahia H (2014), Inhibition effect of potassium iodide on the corrosion of carbon steel (XC 38) in acidic medium. *International Journal of Advanced Chemistry*, 2, 139-142. <https://doi.org/10.14419/ijac.v2i2.3272>.
- [27] Dehri I, Ozcan M (2006), The effect of temperature on the corrosion of mild steel in acidic media in the presence of some sulphur-containing organic compounds. *Materials Chemistry and Physics*, 98,316–323. <https://doi.org/10.1016/j.matchemphys.2005.09.020>.
- [28] Mohamed SM, Mahmoud AA (2015), Some pyrazole derivatives as corrosion inhibitors for carbon steel in hydrochloric acid solutions. *J. eur. chem*, 6, 342-349. <https://doi.org/10.5155/eurjchem.6.3.342-349.1279>.
- [29] Abd El-Rehim SS, Refaey SAM, Taha F, Saleh MB, Ahmed RA (2001), Corrosion inhibition of mild steel in acidic medium using 2-amino thiophenol and 2-cyanomethyl benzothiazole. *Journal of Applied Electrochemistry*, 31, 429–435. <https://doi.org/10.1023/A:1017592322277>.
- [30] David E, Talbot J, James D, Talbot R (2010), Corrosion Science and Technology: Materials Science & Technology. CRC Press, 94-95.