

Study of mechanical and wear characteristics of AL380 composite fabricated by introducing B4C using compo casting method

Ch. V. M. Prasad^{1*}, K. Mallikarjuna Rao²

¹ Department of Mechanical Engineering, Sathya Institute of Technology and Management, Vizianagaram, India

² Department of Mechanical Engineering, JNTU Kakinada, Kakinada, India

*Corresponding author E-mail: prasad354@gmail.com

Abstract

In the present work, Al380 Al alloy and B4C metal matrix composite was fabricated with different weight fractions (1%, 2% and 3%) using compo-casting method. The wear properties of fabricated composite is tested by pin on disc apparatus. On different loads of 30N, 60N and 90N the wear tests are performed. The mechanical properties of hardness and tensile strength are performed on brinell's hardness apparatus and Ultimate tensile machine. The study of homogeneous distribution of B4C particles were examined by scanning electron microscope (SEM) in the composites. The result shows that the Al380 Al alloy reinforced with B4C particles, that composite improves the mechanical properties and wear rate. Increasing of wear rate with the increase in B4C particles in composites. Using Optical microscope, the study of worn surfaces of pins were analyzed.

Keywords: Aluminum; Boron Carbide; Mechanical Properties; Wear Behavior; Compo Casting Method.

1. Introduction

From the past decades in automobile industries, aerospace, defense academy is concentrated on lightweight materials like Al alloys. Because these Al Alloys having Excellent engineering properties like elevated tensile strength, high hardness, better wear resistance and outstanding thermodynamic strength properties. These properties made a remarkable utilization of alloy in various fields. Because of its low-density Al metal matrix composites are very easy to fabricate [1-4]. In general, the SiC, Al₂O₃, TiC, MgO, Zr and AlN particles are used as reinforcement with Al matrix composites [5-10]. B4C is a third hardest material, and it is very expensive so very partial research has been conducted [3], [8]. The B4C is a striking reinforcement because of their properties density (2.52 g/cm³), elevated strength, high hardness and superior wear resistance [12]. Vortex method is the best opted method for bonding of particle matrix where uniform distribution is attained in the reinforcement [23]. This Al metal matrix product affects mechanical properties so it is fit for restricted conditions. There is a dire need of novel material which possesses high hardness, tensile strength and wears resistance, properties that improve the Al metal matrix composites. This is attained by the increase of ceramic particles. The accompaniments of a little quantity tiny proportion of B4C of 5% vol. to Al-7Si-1mg, lead to it an increase of ceramic particles in reinforcement increases the wear resistance [18]. Boron carbide having a good impact, wear resistance and poor wetting time [21]. To improve the Wetting time by pre-treatment of ceramic particles [24]. During casting, K₂TiF₆ halide salt is used to improve bonding between Al and B4C ceramic particles which results improved mechanical properties in

The tailored composite [25]. In this work, at a temperature of 750°C the reinforcement of Al Alloy and B4C was done by using compo-

casting method. During composite preparation, B4C particles are pre-heated up to 1hour before mix and to improve wetting time AD flux was added in the Al molten metal. Further, the composites are prepared as per the experimentation.

2. Experimental procedure

The Table 1. Shows the chemical composition of Al380 Aluminium alloy. In this practice, the matrix material is Al380 aluminium alloy and B4C is a ceramic particle are reinforced. Aluminium alloy density is 2.79g/cm³ and B4C density is 2.52g/cm³ were used in this experimentation. In a graphite crucible, the Aluminium alloy is melted at a temperature range of 700o – 730oC. The B4C ceramic particles are preheated at a temperature of 450oC for 1hour before pouring into the molten Aluminium matrix metal. The pre-heated B4C particles are poured into the crucible and for homogeneous particle distribution in the molten matrix metal, a continuous stirring operation is done for 4-5 minutes at a speed of 600-700 rpm. The cavities formation in the molten liquid can be avoided by using AD flux as minimum range of is 0.25 wt% and maximum range of 1.5wt%. At 900oC the whole mixture is preheated before totaling into the molten metal. 250gms of matrix alloy is heated in a graphite crucible at 750oC temperature. Once the necessary temperature is achieved, AD flux is incorporated to improve the wettability and remove the unwanted gasses from the Al matrix molten liquid. The vortex was generated with the aid of stirrer. The spindle is made up of stainless steel rod rotates with 300-400 rpm for 5-10 minutes. To avoid the problem of clog and separation of particles for getting uniform distribution proper stirring should be carried out before and after addition of the mixture. The process parameters of stir casting are shown in Table 2. As per ASTM E8 standards. The molten metal is poured in Die of length 290 mm,

diameter 10 mm. The same procedure is implemented and cast the composites by varying wt% of 1%, 2%, and 3%.

Table 1: Chemical Composition of A380 Al Alloy

Element	Al	Si	Fe	Cu	Mn	Mg	Cr	Ni	Zn	Ti	Traces
%	--	9.5	1.00	4.00	0.50	0.30	--	0.50	2.90	--	0.50

Table 2: Process Parameter of Stir Casting

Parameters	Data
Melting temperature	8000C
Stirring temperature	700-7300C
Stirrer speed	600-700 rpm
Stirring time after reinforcement	20 min
Incubation time	3 hrs

The process parameters of stir casting are exposed in Table 2. With the aid of compocasting, the molten metal was stirred it for a vortex. The combination of B4C and AD flux are added one after another to the vortex at a stable feed rate. The total mixture was added slowly to the vortex to make sure all particles are dispersed throughout the entire solution for the period of investigational work. Ad flux is to avoid corrosion of Aluminium alloy. The molten metal of total mixture was poured into a cast mold. By varying weight percentage (1%, 2%, and 3%) of B4C, the specimens are prepared as per ASTM E8 standards. The Aluminium metal matrix composite specimens are cooled at room temperature. The Micro structural characterization of the prepared specimen can be examined by Scanning Electron Microscope (SEM) with EDS. The hardness test were conducted by using brinell's hardness tester under a load of 2N with a dwell time of 10 Sec at different locations on the same specimen. With the aid of a Computerized Universal Testing Machine the tensile strength was examined beneath tension. By using computerized pin-on-disc wear testing apparatus the wear test performed on the specimens under different load conditions (30N,60N, and 90N) with constant sliding distance and speed. The load conditions are shown in Table 3. The wear apparatus was cleaned thoroughly with acetone solution. The worn surfaces are examined by Optical Microscope.

Table 3: Test Conditions

Level	Load (N)	Sliding Speed (m/s)	Sliding Distance (mm)	Time (min)
1	30	5.2	100	45
2	60	5.2	100	45
3	90	5.2	100	45

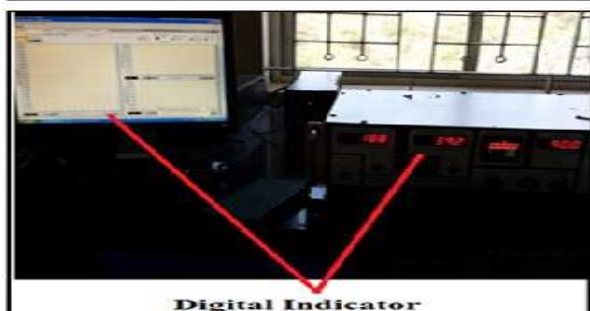


Fig. 1: Pin on Disc Apparatus.

3. Result and discussion

3.1. Evaluation of microstructure

By compo casting method, the reinforcement of Al alloy and B4C are successfully fabricated. Figure.2 a and b shows the Microstructural characterization of fabricated Aluminium metal matrix composite. It observed from the figure that the B4C particles are uniformly distributed in the aluminium matrix it was attained by compo casting. The existence of B4C particles in the corroboration in the matrix is confirmed with Energy Dispersive Spectroscopy.

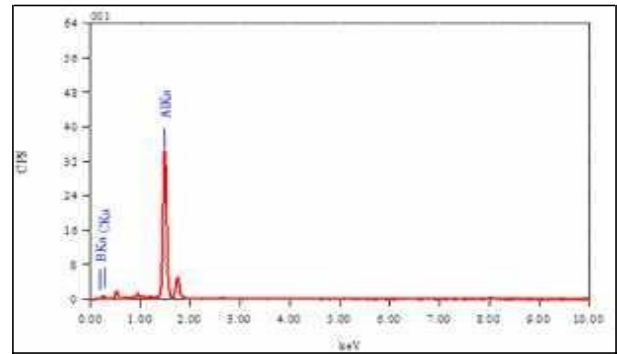


Fig. 2: Optical Micrographs of the As Cast Al Alloy-B4C A) SEM Image of Al- 3 Wtpercentage of B4C B) XRD Pattern of B4C.

3.2. Hardness test results

The Figure.3 shows that the hardness of Aluminium metal matrix composites is increased with the weight percentage of reinforcement. The maximum hardness obtained in the Brinell's hardness for the AMCs is 88 BHN. As compared to the base alloy the hardness is increased in the tailored composite. The existence of B4C particles offers better resistance to deformation which leads to increase the hardness of the tailored composites.

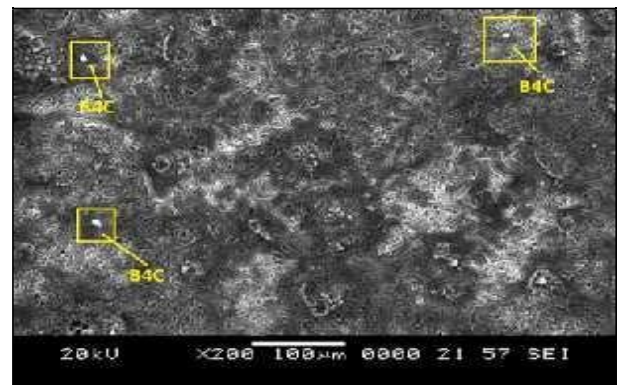


Fig. 3: Hardness of the Cast Al Alloy-B4C with Different WTpercentage.

3.3. Tensile test results

The tensile property was increased in the fabricated metal matrix composite. The Figure.4 shows the tensile strength and Figure.5 shows the elongation of tailored composites of different weight fractions of B4C particles. The improvement of tensile strength is well improved in the composite by incorporating the particles of B4C. while the percentage of B4C is increasing the strength is decreased in the composite. Maximum tensile strength is obtained for Al alloy is 160.16 Mpa and the tensile strength for reinforced composites are found as 132.94 Mpa, 124.91 Mpa and 108.63 Mpa respectively for 1%, 2% and 3% weight percentage of B4C particles. That means the tensile strength decreases because the hardness of composite is increasing

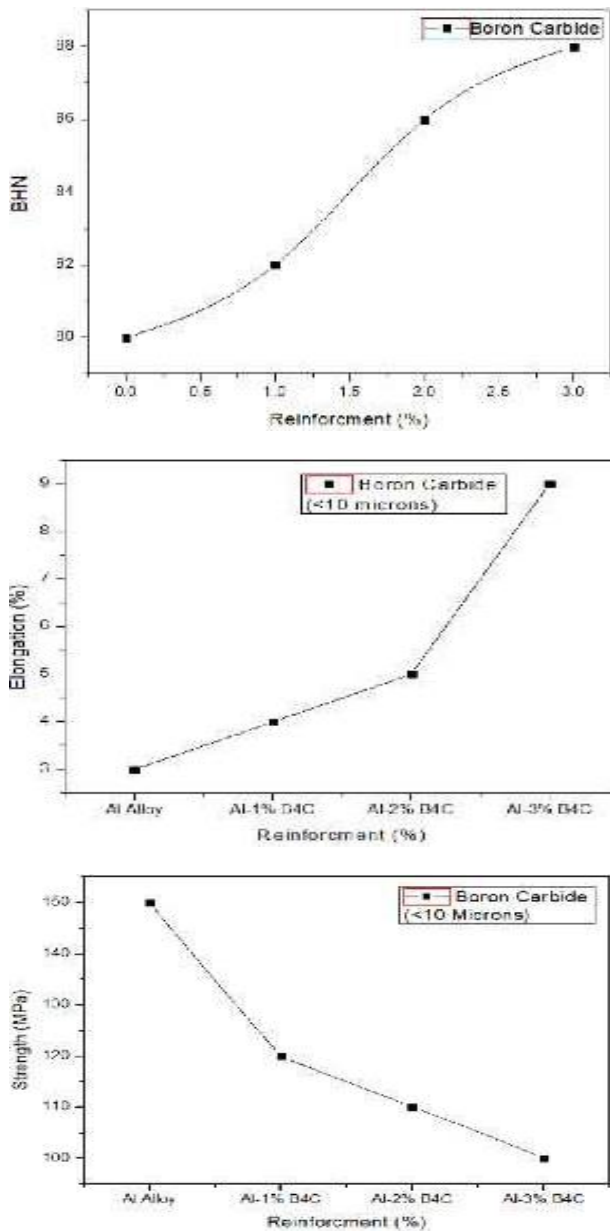


Fig. 4: Tensile Strength of Al+B4C Composites Figure 5: percentage Elongation of Al+B4C Composites.

3.4. Wear test results

The analysis of micro structural of composites are analyzed by Optical Microscope at a constant speed (900 rpm) at different loads (30N, 60N and 90N). at different load conditions the wear tracks are obtained in the Optical Microscope. The images are shown in Figure.6 a, b and c.

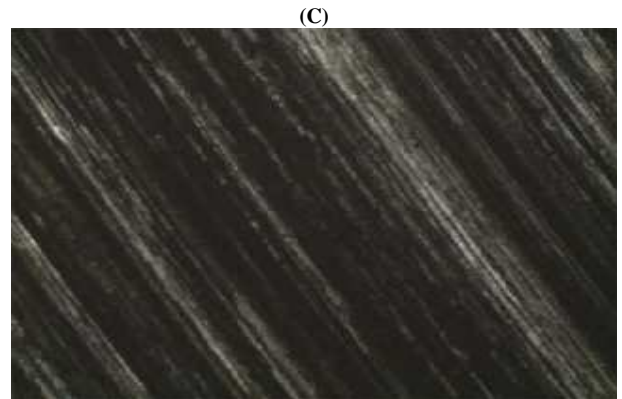
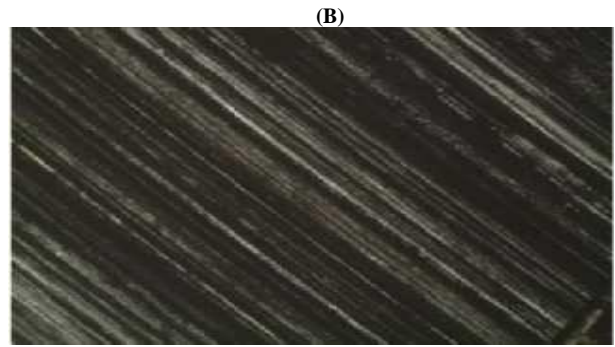
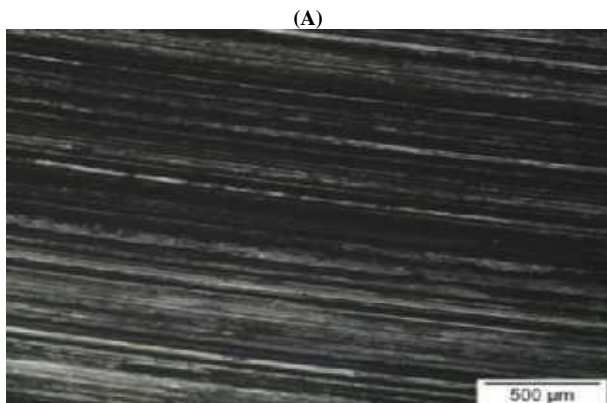


Fig. 6: Microscopic Image of Al/3 % B4C at A Load of A) 30 N, B) 60N and C) 90N.

The wear test samples are prepared as per the ASTM standard. Figure.6 shows the wear rate versus different reinforcement plots at loading conditions of 30N, 60N and 90N. By observing the results the wear rate is increased with the increase of B4C particles. It means the hardness of composite increased by adding of B4C particle in the reinforcement that makes the surface of the composite is brittle that results wear rate is increased. The B4C particles are peels out from the specimen when it touches the disc.

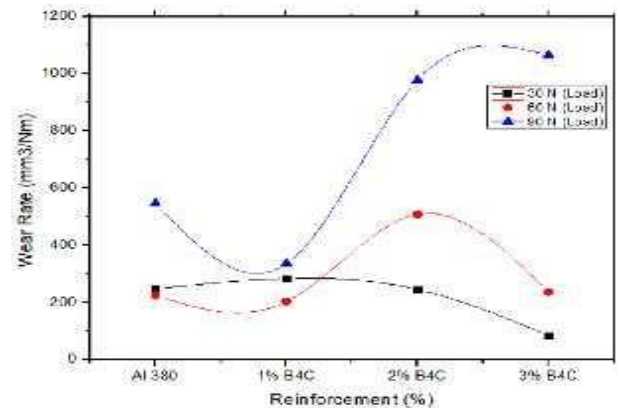


Fig. 7: Varying Load with Al380/B4C.

4. Conclusion

With the particle reinforcement the Al-B4C composites are fabricated by compo-casting method and the microstructure, mechanical and wear properties are evaluated. From the study, the following are concluded.

- Successfully metal matrix composites (Al380-B4C) were fabricated.
- SEM with EDS studies homogeneous dispersion of B4C in the composite.
- The maximum hardness is found in 3 wt% of B4C particles present in AMMC's was obtained by using Brinell's hardness tester.

The tensile strength of AMMC's was found to be maximum for the base material Al380.

- The wear properties are also improved

References

- [1] M.K. Surappa, P. K. Rohatgi (1981), Preparation and properties of cast aluminium-ceramic particle composites, *Journal of materials science*, 16, pp 983-993.
- [2] J.W. Kaczmar, K. Pietrzak, W. Wlosinski (2000), The production and application of metal matrix composite materials, *Journal of material processing technology*, 106, pp:58-67.
- [3] Khan KB, Kutty TRG, Surappa MK. "Hot hardness and indentation creep study on Al-5% Mg alloy matrix-B4C particle reinforced composites," *MaterSciEng A*, 427:76-82, 2006.
- [4] Adamiak M. "selected properties of aluminium alloy base composites reinforced with intermetallic particles". *J Achievements Master ManufEng*, 14(1-2)2006.
- [5] Lee KB, Ahn JP, Kwon H. "Characteristics of AA 6601/BN composite fabricated by pressureless infiltration technique." *Metal Master Trans A*, 32A94:1007-18, 2001.
- [6] Kerti I, Toptan F. "Microstructural variations in cast B4C-reinforced aluminium matrix composites (AMCs)," *Master Lett*: 62:1215- 8, 2008.
- [7] Zhang H, Ramesh KT, Chin ESC. "High strain rate response of aluminium 6092/B4C composites," *Master SciEng A* 384:26- 34, 2004.
- [8] Kalkanli A, Yilmaz S. "Synthesis and characterization of aluminium alloy 7075 reinforced with silicon carbide particulates." *Master Design*, 29:775-80, 2008.
- [9] Ipek R. "Adhesive wear behavior of B4C and Sic reinforced 4147 Al matrix composite (Al/B4C-Al/SiC)." *J Master Proc Technol*, 162- 163:71-5, 2005.
- [10] Kerti I, "Production of TiC reinforced-aluminium composites with the addition of elemental carbon," *Master Lett*, 53:1231-5, 2005.
- [11] Bedir F. "Characteristic properties of Al-Cu-SiCp and Al-Cu-B4Cp composites produced by hot pressing method under nitrogen atmosphere." *Master Design*, 28:1238-44, 2007.
- [12] R.M. Mohanty, K. Balasubramanian, S.K. Seshadri, "Boron carbide-reinforced aluminium 1100 matrix composites: fabrication and properties," *Materials science and engineering*, 498, pp42-52, 2008.
- [13] K.H.W. Seah, J. Hemanth, S.C. Sharma, "Mechanical properties of aluminium/quartz particulate composites cast using metallic and nonmetallic chills," *Materials and design*, 24, pp 87-93, 2003.
- [14] M.A. Belger, P.K Rohatgi, N. Gupta, "Aluminium composite casting incorporating used and virgin foundry sand as particle reinforcements, solidification processing of metal matrix composites-Rohatgi honorary symposium," *TMS Annual Meeting*, pp 95-104, 2006.
- [15] S. Sulaiman, M. Sayuti, R. Samin, "Mechanical properties of the as cast quartz particulate reinforced LM6 alloy matrix composites," *Journal of materials processing technology*, 201, pp 731-735, 2008.
- [16] T.R. Chapman, D.E. Niesz, R.T. Fox, T. Fawcett, "Wear-resistant aluminium-boron-carbide cermets for automotive brake applications," *Wear*, 23, pp 81-87, 1999.
- [17] W.R. Blumenthal, G.T. Gray, T.N. Claytor, "Response of aluminium-infiltrated boron carbide cermets to shock wave loading," *Journal of material science*, 29/17, pp 4567-4576, 1994.
- [18] Chandrashekar B R, Prakash A M, K S Badarinarayan, Madeva Nagaral, Reddappa H N, Hardness and wear behavior of B4C particulates reinforced al-7si-1mg alloy composites, *International Journal of Engineering Research*, Vol No.5 Issue 6, p 1129 – 1254, 2016.
- [19] Hashim J. Looney L and Hashmi M.S.J, "Metal matrix composites: production by the stir casting method", *J. Mater. Process, Technol.* 92/93, 1, 1999.
- [20] Sallahuddin Attar, Madeva Nagaral, H. N. Reddappa, and V. Auradi, "Effect of B4C Particulates Addition on Wear Properties of Al7025 Alloy Composites", *American Journal of Materials Science*, 5(3C), pp.53-57, 2015.
- [21] Canakci A., Fazil Arslan and Ibrahim Yasar, 2007. "Pre-treatment process of B4C particles to improve incorporation into molten AA2014 alloy" *J Mater Sci*, 42, 9536.
- [22] Canakci A., 2011. "Microstructure and abrasive wear behavior of B4C particle reinforced 2014 Al matrix composites", *J. Mater. Sci.*, 46 (08), 2805.
- [23] Ch.V.M.Prasad, K.Malli Karjuna Rao, "Fabrication and Characterization of B4Cp Particle Reinforcement LM24 Al Alloy composites", *International Journal For Research In Applied Science And Engineering Technology*, Vol.4 ,pp 120-130, 2016.
- [24] Kennedy A.R, Brampto B., 2001. "The reactive wetting and incorporation of B4C particles into molten aluminium," *Scripta Mater*, 44, 1077.
- [25] Kalaiselvan K., Murugan N., Siva Parameswaran. 2011. "Production and characterization of 6061Al-B4C stir cast composite", *Material and Design* 32, 4004.