



# Experimental investigation on mechanical behaviour and parameters of FDM printed carbon fibre reinforced PET-G and PET-G

Kareem Dakhil Jasym \*

Department of Mechanical Engineering, AL-Qadissiya University College of engineering , Iraq

\*Corresponding author E-mail: [kareemadli9@gmail.com](mailto:kareemadli9@gmail.com)

## Abstract

In present study tests like Tensile, Compression and Flexural on the 3D Printed standard specimens of PETG and CARBON FIBER REINFORCED is carried on PETG by changing the printing parameters to find their mechanical properties by using FDM. The experimental results indicated that the tensile strength of carbon fiber reinforced pet-G is 1.28% higher than pure PET-G sample. Its optimum value is observed from Taguchi L9 to be 30.804 from SN curve and same as 34.629 in MEAN curve. The variation in the two values is noticed to be 12.12 % for SN curve and 0 % in case of MEANS Carbon fiber PET-G specimen with 300 $\mu$  layer thickness, 80% infill density, 60 mm/sec print speed had the largest mean value of tensile strength. The ultimate tensile strength of fabricated specimen with 300 $\mu$  layer thickness, 80% infill density, and 60 mm/sec print speed could increase 1.28% when compared with pure PET-G specimen.

**Keywords:** 3D printing; Biodegradable Polymers; Fabrication; FDM; PET-G; Testing.

## 1. Introduction

In recent years, biodegradable companies are drawing attentions in aerospace applications because of serious environmental problem which are cause due to thermosetting composite. Osgouei et al reviewed the application of environmental polymers and came to conclusion biopolymers can offer environmental benefits such as biodegradability and renewability [1]. Polyethylene terephthalate (PET-G) is a biodegradable and eco-friendly material having good-mechanical properties. 3D printing method is widely investigated in processing the thermoplastic resin of PETG due to the good characteristics of strong operation, low cost and no need of tooling or mold. Lithography Apparatus (SLA) and Fused Deposition Modelling (FDM) are two printing techniques [2]. For industrial production fused deposition modelling is a better choice with low cost of printing device and thermoplastic materials. Various types of devices are printed using FDM. Hopkinson, N& Dickens have introduced materials that are appropriate for final manufacture, which has in turn introduced the possibility of directly manufacturing finished components [3]. Hutmacher et al. (2001) and Ahn et al. (2002) investigated the mechanical strength and anisotropic properties of devices or parts produced using FDM technique [4][5]. Matsuzaki et al. (2016) investigated that continuous fiber reinforced composites can be fabricated and manufactured using 3D printing and this technique has the potential to become the methodology for next generation [6]. Mori et al. (2014) printed a sandwich structure with carbon fibers placed between lower and upper plastic plates and heated after 3D printing to bond the carbon fibers with the plastics [7]. These printing methods mention above can manufacture continuous carbon fiber reinforced thermoplastic composites. However the major disadvantages is the weak infiltration and between fiber and resin which can reduce the performance of printed composites.

To develop the continuous carbon-fibre re-enforced PET-G composites with curved structures and with higher mechanical strength a proto-typing approach has been proposed in this paper which can be used for rapid and continuous printing. Rapid proto-typing refers to a class of technologies in which physical models can be automatically constructed using CAD data. The key idea of rapid prototyping technology is based on decomposition of 3-D computer models into thin cross-sectional layers, followed by physically forming the layers and stacking them up "layer by layer." [8] Mansour, and Saleh N investigation into the advent of Rapid Manufacturing in influencing an individual designer's approach to product design and materials selection is detailed. [9] Bitzez developed adaptive design technologies by investigating current design methods and knowledge of deployable technologies in the area of engineering design and manufacturing [10] John K Borchardt used unmanned aerial vehicles spur composite, keeping flight time of the UAV's in mind, the UAV's are made of light but durable materials. And new composites that are being developed make use of high molecular weight polyethylene, S glass, E glass, aramid, quartz, bismaleimide and graphite fibers reinforcing epoxy, polyester, vinyl ester, phenolic and polyimide resins. [11]

### 1.1. Methodology of rapid prototyping

The basic methodology of for all current rapid prototyping techniques is almost same with some variation .A cad model is designed and constructed and the cad model is converted into .stl format [12]. The Rapid prototyping machine can process the .stl model by creating



sliced layers of the model. The model is then lowered by the thickness of the next layer, and the process is repeated until the completion of the layer. The surface of the model is cleaned at the last

## 1.2. Designing of 3d printing

The first step in generating any FDM part is to create a three dimensional solid model. The stl format is used because it simplifies the geometry by the reducing it to most basic components. Once the stl part is created it is exported to slicer where it is horizontally sliced into many thin sections.

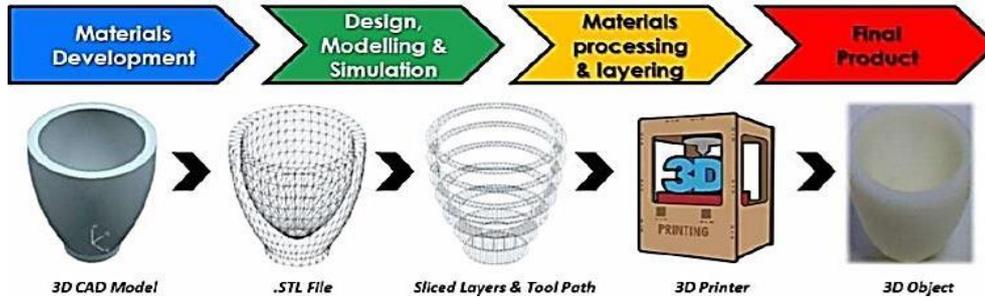


Fig. 1: Process of 3D Printing.

## 2. Fabrication and experimental

Three different types of specimen are modelled in stl format and fabricated using FDM machine. FDM works on an "additive" principle by laying down material in layers; a plastic filament or metal wire is unwound from a coil and supplies material to produce a part. FDM begins with a software process which processes an STL file (stereolithography file format). During the pre-processing stage, the wall thickness of the CAD model was offset so as to account for the metal foil thickness that would be realised during the deposition phase. Figure 2 and 3 shows the ASTM standard dimensions for the samples fabricated. Figure 4 shows schematic diagram of 3D printing machine and 3D printer used for printing the specimen. Figure 5 shows the specimens which are printed by the 3D printer. These specimens will be used for the testing the mechanical properties.

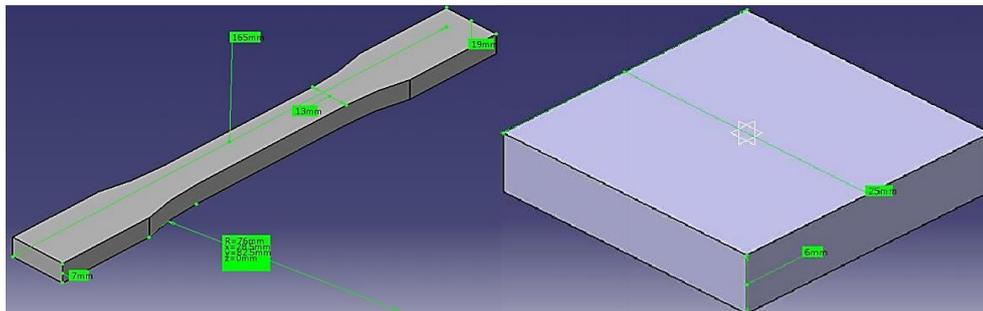


Fig. 2: Process of 3D printing.

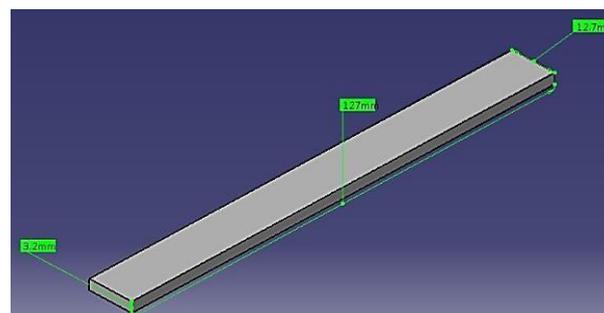


Fig. 3: Design of Specimen.

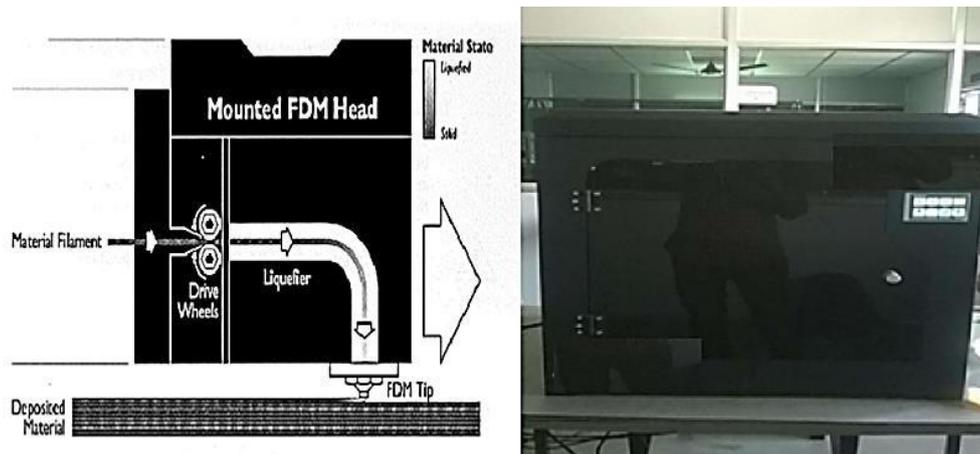


Fig. 4: Schematic Diagram of 3D Printer (Left) and 3D Printer (Right).




Fig. 5: 3D Printed Specimen before Testing.

## 2.1. Testing of fabricated design

Since the work is on testing Carbon fiber reinforced Pet-G for MAV applications 3d printing nine samples specimens ASTM D638 of different parameters according to Tguchi L9 method and comparing the largest outcome with Pet-G and also testing the carbon fiber reinforced Pet-G with the same parameter by conducting flexural ASTM D790 and shore hardness test ASTM D785. Three types of tests will be performed in accordance with ASTM standard on an universal Testing Machine of 60 T capacity as shown in figure 7. The test specimen was first conditioned at  $23 \pm 2$  and at  $50 \pm 5$  relative humidity for not less than 40 h prior to the test. The width and thickness of each specimen to the nearest 0.025 mm [0.001] was measured. The width and thickness measurements at the center of each specimen were also made within each end of the gage length.

### 2.1.1. Ultimate tensile testing

Specimens were placed in the grips of the Universal testing machine, taking care to align the long axis of the specimen and the grips with Imaginary line joining the points of attachment of the grips to the machine. The testing between the ends of the surface was noted and set according to the standard. The grips were tightened evenly and firmly then, a Calibrated extensometer was attached to the specimen and gage length. The crosshead speed was set to 50mm/min and the machine was started, during testing the inbuilt software records and plots the load- extension curve of the specimen using which the properties such as tensile strength, Young modulus and elongation at break were then calculated and recorded

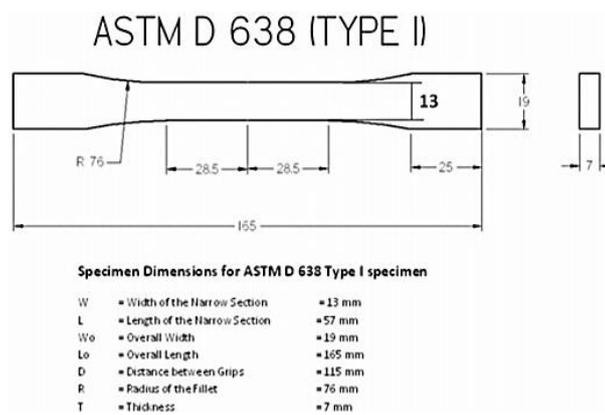

**Fig. 6:** Dimensions of Specimen According to ASTM.



**Fig. 7:** Mechanical Tests Conducted on 60T UTM (Tensile Test).

### 2.1.2. Flexure testing

The stress-strain behavior of polymers in flexure is of interest to a designer as well as a polymer manufacturer. Flexural strength is the ability of the material to withstand bending forces applied perpendicular to this longitudinal axis. The flexural modulus is a measure of the stiffness during the first or initial part of the bending process. The value of flexural modulus is, in many cases equal to the tensile modulus. The flexural test was carried out using an UTM machine according to ASTM D790. Since the modulus was determined between small initial deflections, a low force load cell (100N) was used to ensure good accuracy. Flexural test were carried out using a simple supported beam. The distance between the spans is 100mm and a crosshead speed of 3mm/min was used. The test was carried out at room temperature. In this research, five samples were tested for each composition and average values were recorded. Flexural toughness was calculated from the area under stress- strain curve.



**Fig. 8:** Flexural Testing Machine (60T UTM) Hardness Test.

### 2.1.3. Hardness testing

Hardness is a characteristic of a material, not a fundamental physical property. It is defined as the resistance to indentation, and it is determined by measuring the permanent depth of the indentation. Figure 8 shows hardness testing machine used for testing hardness of the specimens.



**Fig. 9:** Flexural Testing Machine (60 T UTM).

### 3. Results and discussions

#### 3.1. Tensile test results

The tensile load is gradually applied till the specimen is broken at the average max. Values of 1.68 - 2.98 KN. The load then falls to zero. The maximum tensile strength obtained for Carbon Fiber Pet-G from the experimental value is 34.629 MPa. Its optimum value is observed from Taguchi L9 [13] to be 30.804 from SN curve [14] and same as 34.629 in MEAN curve. The variation in the two values is noticed to be 12.12% for SN curve and 0 % in case of MEANS. Tensile test results. The maximum tensile strength obtained for Carbon Fiber Pet-G and for PET- G from the experimental value is 34.629 MPa and 34.192 MPa respectively, where the variation is noticed to be 1.28% increase in Carbon fiber PET-G. Figure 10 shows the carbon-reinforced PET-G samples after the tensile test been performed on them. .Figure 10, Figure 11 shows PET-G sample after the tensile test been performed on them. Figure 12 shows the ultimate strength of 9 different samples for testing and comparison of ultimate strength of carbon-reinforced PET-G sample and PET-G sample.



**Fig. 10:** Tensile Specimens after Testing (Carbon Fiber PET -G).




**Fig. 11:** Tensile Specimen after Testing (PET-G).

Note: At 300 microns, 80 %, 60 mm/sec we got more ultimate load as well as ultimate tensile strength. So, we performed tensile test on PET-G and flexural, shore hardness tests on carbon fiber Pet-g with same parameter

**Table 1:** Mechanical Properties of Carbon Fiber Pet-G Tensile Specimen

Sample No.	Ultimate Load (KN)	Ultimate Tensile Strength
1	2.7	29.466
2	2.7	30.030
3	2.28	25.244
4	2.58	31.174

5	2.34	28.481
6	1.68	20.005
7	2.94	34.629
8	2.28	27.049
9	1.98	23.571

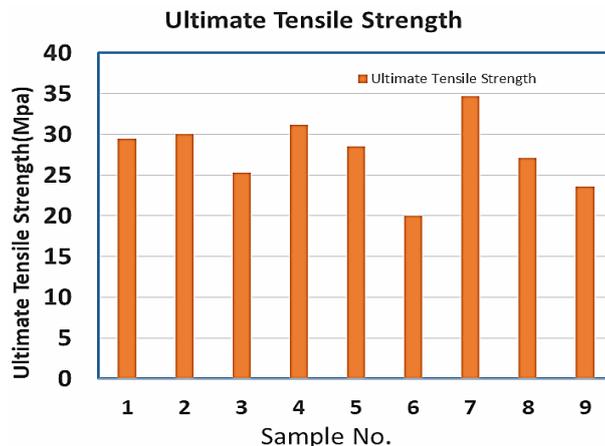

COMPARISON OF PET-G AND CARBON FIBER  
PET-G AT 300μ, 80%, 60 mm/sec

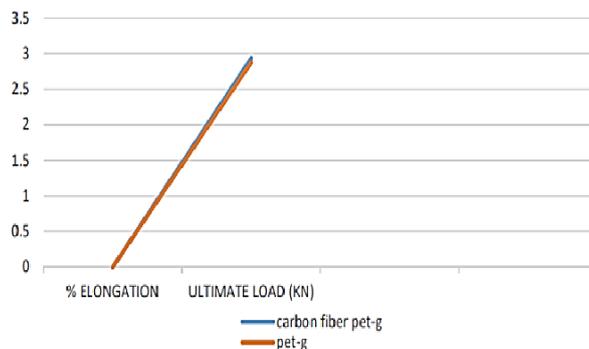


Fig. 12: Ultimate Strength of Tensile Specimens and Comparison of Ultimate Load in KN.

3.2. Flexural test results

The flexural strength obtained by experimental analysis is 255.08N/mm<sup>2</sup>. This flexural test is performed under maximum parameter which is obtained in tensile test i.e., at 300μ, 80%, 60 mm/sec. Figure 13 shows flexural tested specimen before and after the been performed.

Table 2: Flexural Test Results

S. NO.	Specimen	Load P(N)	L(mm)	3PL	b(mm)	D(mm)	d*d	2bd <sup>2</sup>	Flexural Strength (N/mm <sup>2</sup> )
1	300μ, 80%, 60mm	480	50	72000	13.28	3.26	10.6276	282.27	255.08

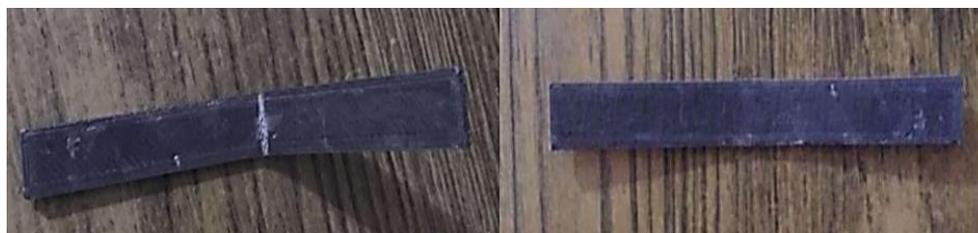


Fig. 13: Flexural Tested Specimen.

3.3. Hardness test results

Total test forces range from 15kgf to 150 kgf (superficial and regular) to 500 to 3000 kgf (macro hardness). This test procedure is carried out on a standard block of ASTM D 2240:2003 The hardness number is observed in case of Carbon Fiber Pet-G is 52, 52, and 53 respectively. Figure 14 shows specimen before and after hardness tests been performed.

Table 3: Shore Hardness Values

S/NO.	SPECIMEN	SHORE HARDNESS(D)
1	300μ,80%,6mm/sec	52,52,53



Fig. 14: Specimen Before and after Hardness Test.

## 4. Conclusions

In this study, CFRP composite filaments were directly available in the form of carbon-fiber reinforced Pet-G in which it can also be prepared from extrusion processes. FIBER REINFORCED is carried on PETG by changing the printing parameters to find their mechanical properties by using FDM. The experimental results indicated that the tensile strength of carbon fiber reinforced pet-G is 1.28% higher than pure PET-G sample. Its optimum value is observed from Taguchi L9 to be 30.804 from SN curve and same as 34.629 in MEAN curve. The variation in the two values is noticed to be 12.12 % for SN curve and 0 % in case of MEANS Carbon fiber PET-G specimen with 300 $\mu$  layer thickness, 80% infill density, 60 mm/sec print speed had the largest mean value of tensile strength. The ultimate tensile strength of fabricated specimen with 300 $\mu$  layer thickness, 80% infill density, 60 mm/sec print speed could increase 1.28% when compared with pure PET-G specimen. Materials with high strength to weight ratio like Carbon Fiber composite materials can be used to manufacture light weight parts which can be used to produce MAV's and also to replace some parts in other beneficiary industries.

## References

- [1] Alizadeh-Osgouei M, Li Y, Wen C. A comprehensive review of biodegradable synthetic polymer-ceramic composites and their manufacture for biomedical applications. *Bioact Mater.* 2018; 4(1):22-36. Published 2018 Nov 27. <https://doi.org/10.1016/j.bioactmat.2018.11.003>.
- [2] Yan X, Gu P (1996) A review of rapid prototyping technologies and systems. *Comput Aided Des* 28(4):307–318 [https://doi.org/10.1016/0010-4485\(95\)00035-6](https://doi.org/10.1016/0010-4485(95)00035-6).
- [3] Hopkinson, N & Dickens, P 2006, 'Emerging Rapid Manufacturing Processes', in *Rapid Manufacturing; An industrial revolution for the digital age*, Wiley & Sons Ltd, Chichester, W. Sussex. <https://doi.org/10.1002/0470033991.ch5>.
- [4] Hutmacher, D.W., Schantz, T., Zein, I., Ng, K.W., Teoh, S.H. and Tan, K.C. (2001), "Mechanical properties and cell cultural response of polycaprolactone scaffolds designed and fabricated via fused deposition modelling", *Journal of Biomedical Materials Research: Part A*, Vol. 55 No. 2, pp. 203-16. [https://doi.org/10.1002/1097-4636\(200105\)55:2<203::AID-JBM1007>3.3.CO;2-Z](https://doi.org/10.1002/1097-4636(200105)55:2<203::AID-JBM1007>3.3.CO;2-Z).
- [5] Ahn SH, Montero M, Odell D, Roundy S, Wright PK (2002) Anisotropic material properties of fused deposition modeling ABS. *Rapid Prototyp J* 8(4):248–257. <https://doi.org/10.1108/13552540210441166>.
- [6] Matsuzaki R, Ueda M, Namiki M, et al. Three-dimensional printing of continuous-fiber composites by in-nozzle impregnation. *Sci Rep.* 2016; 6:23058. <https://doi.org/10.1038/srep23058>.
- [7] Published 2016 Mar 11. <https://doi.org/10.1038/srep23058>.
- [8] K. I. Mori, T. Maeno, and Y. Nakagawa, "Dieless forming of carbon fibre reinforced plastic parts using 3D printer," in *Procedia Engineering*, 2014, pp. 1595-1600. <https://doi.org/10.1016/j.proeng.2014.10.196>.
- [9] B.E.Fischer, and H.Sigel, *J.Am.Chem.Soc.*, 102(9) (1980) 2998-3008. <https://doi.org/10.1021/ja00529a021>.
- [10] Hague R, Mansour S, and Saleh N, 2004, "Material and design considerations for rapid manufacturing", *International Journal of Production Research*. <https://doi.org/10.1080/00207840410001733940>.
- [11] Bitzer, T., "Honeycomb Technology: Materials, Design, Manufacturing, Applications and Testing," Springer, 1997. [11] John K Borchardt Unmanned aerial vehicles spur composites use Reinforced Plastics, Volume 48, Issue 4, April 2004, Pages 28-31 [https://doi.org/10.1016/S0034-3617\(04\)00194-8](https://doi.org/10.1016/S0034-3617(04)00194-8).
- [12] Z Zhou, D Li, J Zeng and Z Zhang, Rapid fabrication of metal-coated composite stereo lithography parts, *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture* (2007), Vol. 221, pp.1431-1440. <https://doi.org/10.1243/09544054JEM827>.
- [13] Kuo Y, Yang T, Huang GW (2008) the use of grey-based Taguchi method to optimize multi-response simulation problems. *Eng Optim* 40(6):517–528 <https://doi.org/10.1080/03052150701857645>.
- [14] Minitab Statistical Software Features – Minitab." *Software for Statistics, Process Improvement, Six Sigma, Quality – Minitab.* N.p., n.d. Web. 11 Apr. 2011.